



Standard Test Method for Determining Strength of Gap-Filling Adhesive Bonds in Shear by Compression Loading¹

This standard is issued under the fixed designation D 3931; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (€) indicates an editorial change since the last revision or reapproval.

€¹ NOTE—Keywords were added in April 1999.

1. Scope

1.1 This test method covers the determination of comparative shear properties of gap-filling adhesives in wood-to-wood joints at specified thicknesses of bondline in the dry condition, when tested on standard specimens under specified conditions of preparation, conditioning, and loading in compression. This test method is intended as an evaluation of gap-filling adhesives such as those used to bond plywood to lumber, lumber to lumber, and other similar materials in building constructions.

1.2 This test method also may be used to determine shear properties of gap-filling adhesives in species of wood and in thicknesses of bondline other than those specified for the comparative tests of shear properties within this test method. All procedures specified herein are applicable, excepting requirements for wood species and specific gravity, and thicknesses of bondlines.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:

- D 143 Methods of Testing Small Clear Specimens of Timber²
- D 905 Test Method for Strength Properties of Adhesive Bonds in Shear by Compression Loading³
- D 1151 Test Method for Effect of Moisture and Temperature on Adhesive Bonds³
- E 171 Specification for Standard Atmospheres for Conditioning and Testing Materials⁴

3. Terminology

3.1 Definitions:

¹ This test method is under the jurisdiction of ASTM Committee D-14 on Adhesives and is the direct responsibility of Subcommittee D14.70 on Construction Adhesives.

Current edition approved Dec. 15, 1993. Published February 1994. Originally published as D 3931 – 80. Last previous edition D 3931 – 90.

² *Annual Book of ASTM Standards*, Vol 04.10.

³ *Annual Book of ASTM Standards*, Vol 15.06.

⁴ *Annual Book of ASTM Standards*, Vol 15.09.

3.1.1 *gap-filling adhesive, n*—an adhesive capable of forming and maintaining a bond between surfaces that are not close-fitting.

3.1.1.1 *Discussion*—Close-fitting is relative to a given material and industry; for example, standards in construction differ from standards in electronics. Some adhesives will bond by bridging without completely filling the gap; others by filling the gap completely.

4. Significance and Use

4.1 Structural design based on strength-of-materials principles requires knowledge of the mechanical properties of the structural components, including adhesives. By nature of their use, the most important property of adhesive is shear strength.

4.2 Shear strength measured by this test method is suitable for use in adhesive development, manufacturing quality control, and in materials performance specifications, as well as structural design.

5. Apparatus


5.1 *Testing Machine*, having a capacity of about 15 000 lb (6818 kg) in compression or of sufficient capacity to test the adhesive in use. The machine shall be fitted with a shearing tool containing a self-aligning seat to ensure uniform lateral distribution of the load. The machine shall be capable of maintaining a uniform rate of loading such that the load may be applied with a continuous motion of the movable head to maximum load at a rate of 9.20 in. (5.0 mm)/min with a permissible variation of $\pm 25\%$. The shearing tool shown in Fig. 1 of Test Method D 905 has been found satisfactory. Locate the testing machine in an atmosphere such that the moisture content of the specimens, developed under the conditions prescribed in 7.3, is not noticeably altered during testing.

6. Test Specimen and Sample

6.1 Test specimens for adhesive bonds shall conform to the form and dimensions shown in Fig. 1. Prepare bonded assemblies as described in 7.1. Prepare test specimens for testing as described in 7.2.

6.2 Determine mean shear strengths of bonds at bondline thicknesses of 0.006 and 0.060 in. (0.15 and 1.52 mm). Tests

TABLE 1

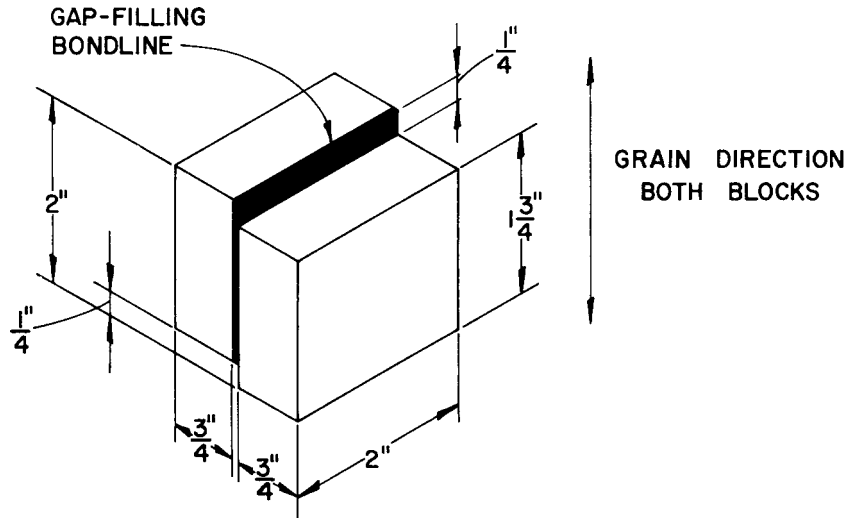

Metric Equivalents

in.	0.064	1/4	3/4	1 3/4	2
mm	1.63	6.35	19.05	44.45	50.80

FIG. 1 Form and Dimensions of Test Specimen

for strengths of bonds at other thicknesses, in addition to those specified, shall be optional upon agreement between the manufacturer and the user.

6.3 Test a minimum of 28 specimens, representing seven different bonded assemblies, to determine mean shear strengths of bonds at each bondline thickness.

7. Procedure

7.1 Preparation of Bonded Assemblies:


7.1.1 Prepare bonded assemblies with hard maple blocks (*Acer saccharum* or *Acer nigrum*) conditioned as described in 7.3. The blocks shall have a minimum specific gravity of 0.65, based on oven-dry weight and oven-dry volume (Note 1).

NOTE 1—A method for selecting maple blocks of satisfactory specific gravity is described in the Appendix of Test Method D 905. For reference

tests, the specific gravity of blocks may be determined in accordance with the Weight and Moisture Content Section under Nail Withdrawal of Test Methods D 143.

7.1.1.1 These blocks shall be straight-grained and free of defects, including knots, splits, birdseye, short grain, decay, and any unusual discoloration within the shearing area. The blocks shall be of suitable size so that four test specimens can be cut from one test joint, as shown in Fig. 2. Blocks approximately 3/4 by 2 1/2 by 14 in. (19 by 63 by 356 mm) have been found to be satisfactory for this purpose. The moisture content shall be from 8 to 10 % (conditions prescribed in 7.3.1) based on oven-dry weight as determined on representative samples in accordance with the final measurement section under radial and tangential shrinkage and the weighing section under moisture determination in Test Methods D 143. Surface

TABLE 2

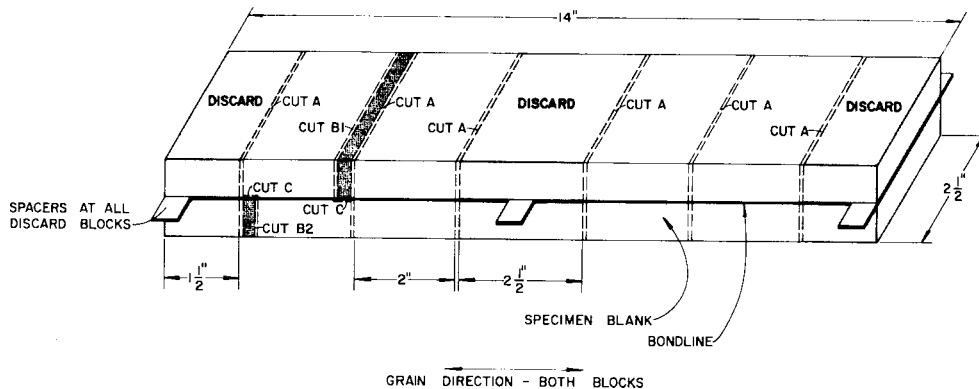

Metric Equivalents

in.	1 1/2	2	2 1/2	14
mm	38.1	50.8	63.5	356.0

FIG. 2 Bonded Assembly Showing Method of Cutting Four Test Specimen Blanks

the blocks just prior to gluing, preferably with a hand-fed jointer. Make sure the surfaces remain unsanded and free from dirt.

7.1.2 Use spacer strips to control bondlines to specified thicknesses between blocks. Spacers shall be wood veneer or plastic, and measure approximately ½ by 3½ in. (13 by 89 mm) long. Place spacers crosswise at the ends and center of the lower test joint block. Apply adhesive in sufficient quantity to ensure squeezeout at the ends of the joint when blocks are under pressure (Note 2).

NOTE 2—If the adhesive is to be applied as an extruded bead, the bead should be ⅜ to ½ in. (10 to 13 mm) in diameter to ensure squeezeout in bondline thicknesses near 0.060 in. (1.5 mm). Use a smaller diameter bead of adhesive for thinner bondlines.

7.1.2.1 Take care to avoid air entrapment in the bondline. Do not spread the adhesive closer than ½ in. (13 mm) to any spacer because adhesive may be entrapped between block and spacer, thereby increasing bondline thickness. Assemble the blocks immediately, unless specified otherwise by agreement between the manufacturer and user of the adhesive. Apply a 15-lb (7.0-kg) load uniformly over the entire bond area to ensure firm contact between spacers and blocks of the assembly. Maintain the pressure on test joints at the conditions prescribed in 7.1.

7.1.3 Curing time for bonded assemblies shall be as specified by the manufacturer of the adhesive, or else 30 days in the standard atmosphere (7.3.1).

7.2 Preparation of Test Specimens:

7.2.1 Joint one edge of each bonded assembly to use as a reference surface in further cutting. Rip-saw the other edge to reduce the width of the assembly to 2 in. (51 mm). Cut 2-in. long specimen blanks with the reference surface of the bonded assembly against the crosscut guide of the saw (Cut A, Fig. 2). Then using a stop clamped to the crosscut guide, notch each end of the specimen blank to achieve the 1¾-in. (44.5-mm) bond length (Cuts B1 and B2, Fig. 2). Always make the cut with the reference surface against the crosscut guide. Make Cut B1 extend through the laminate to the glue line. Make Cut B2 extend through the laminate and through the glue line. The purpose of the latter procedure is to ensure that the adhesive-adhered bond under test is aligned with the shear plane. Make the final cuts (Cut C, Fig. 2) with the block vertical in order to remove waste and complete the steps on either end of the specimen. Keep the reference surface against the crosscut guide. Take special care in making all of the above cuts to ensure that the loading surfaces are smooth, parallel to each other, and perpendicular to the edges and the bondline.

7.2.2 Measure and record the bond width and length to the nearest 0.010 in. (0.25 mm).

7.3 Conditioning:

7.3.1 Use the standard atmosphere for adhesives for conditioning wood blocks prior to bonding, curing of test joints, and storing of test joints and specimens prior to testing, unless otherwise specified. The standard atmosphere (Specification E 171) is a relative humidity of 50 ± 5 % and a temperature of 73.4 ± 3.6°F (23 ± 2°C). Store wood blocks, test joints, and specimens at these conditions for a period of 7 days, or until they reach equilibrium moisture content as indicated by no

progressive changes in weight.

7.3.2 Other conditions such as described in Test Method D 1151 in materials performance specifications, or by mutual agreement between the parties of the test, may be used in addition to the standard atmosphere.

7.4 Testing—Place the test specimen in the shearing tool so that the load may be applied as described in 5.1. The position of the specimen with respect to the loading ledge and self-adjusting bearing is shown in Fig. 3. Take special care to ensure that the maple block rests on the lower ledge bearing and abuts the gap-filling bondline. The upper self-adjusting bearing should rest on the opposite maple block and gap-filling bondline. Apply the loading with a continuous motion of the movable crosshead at a rate of 0.20 in./min (5.0 mm/min) to failure as described in 5.1.

8. Calculation

8.1 Calculate the nominal shear stress at failure in pounds-force per square inch (or pascals), and estimate the percentage of wood failure based on the measured bondline area between the two laminations. Record for each specimen.

8.2 Calculate the mean of the specimens of each group tested as:

$$\bar{x}_i = \Sigma x_i / n \quad (1)$$

where:

\bar{x}_i = mean shear strength,

x_i = individual shear strengths of specimens in a group, and

n = number of specimens in the group.

8.3 Calculate the standard deviation of the group as:

$$s = \sqrt{\Sigma \bar{x}_i^2 - [(\Sigma x_i)^2 / n] / (n - 1)} \quad (2)$$

8.4 Calculate the standard error of the mean as:

$$s_{\bar{x}} = \sqrt{s^2 / n} \quad (3)$$

8.5 Calculate the mean percentage of wood failure, as shown in 8.2.

9. Report

9.1 Report the following information:

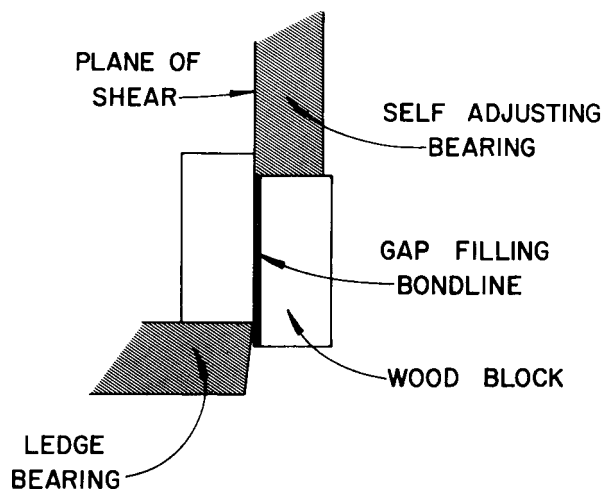


FIG. 3 Side View of Test Specimen Showing Method of Notching Specimen to Ensure Proper Alignment of Shearing Tool and Plane of Shear

9.1.1 Complete identification of the adhesive tested, including type, source, manufacturer's code numbers, form, etc.

9.1.2 Type of adherends in test specimens; that is, species, specific gravity, and grain orientation (that is, edge or flat grain).

9.1.3 Bondline thicknesses tested, as determined from thicknesses of spacers used rather than measured thickness of cured bondline.

9.1.4 Moisture content of wood at time of bonding, method of adhesive application, and time of cure.

9.1.5 Temperature and relative humidity used for preconditioning wood blocks, curing of adhesive, and testing of specimens.

9.1.6 Number of specimens tested at each bondline thickness.

9.1.7 Number of test joints represented at each bondline thickness.

9.1.8 The mean, maximum, and minimum shear stresses at failure, and mean percentage of wood failure for each bondline thickness. Also report the standard deviation of test values for shear stress at failure. Individual test values may be included in the report at the option of either manufacturer or user.

10. Precision and Bias

10.1 Precision:

10.1.1 At the present time there is no basis for a statement of precision concerning the reproducibility of results among

laboratories. Such information may be available in the future following round-robin testing among laboratories.

10.1.2 The precision of the test is a function of the properties of the cured bondline; and if wood failure occurs, it is a function of the wood's variability. Precision shall be reported in terms of the standard deviation of the data and the standard error of the mean.

10.2 *Bias*—The ability of this test method to measure the pure shear strength of the bond has not been established. The test is similar in principle to the method for the shear strength of wood parallel to the grain described in the Shear Parallel to Grain portion of Test Methods D 143. The latter method has been found to yield shear strength values close to the pure shear strength of wood due to offsetting factors of stress concentrations in the specimen and friction in the shear tool.⁵ For this reason the shear strengths of flexible adhesives that can relieve stress concentrations may yield shear values somewhat higher than the pure shear strength when tested by this test method.

11. Keywords

11.1 adhesive; gap-filling; shear strength

⁵ Norris, C.B., "Comparison of Standard Block-Shear Test with the Panel-Shear Test," *Forest Products Journal* Vol 7, No. 9, 1957, pp. 299–301.

The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, 100 Barr Harbor Drive, West Conshohocken, PA 19428.

This standard is copyrighted by ASTM, 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (<http://www.astm.org>).